

AWARD NUMBER: W81XWH-13-1-0240

TITLE: Targeted, On-Demand Charge Conversional Nanotherapeutics for Advanced Prostate Cancer

PRINCIPAL INVESTIGATOR: Xuli Wang, Ph.D.

CONTRACTING ORGANIZATION: The University of Utah
Salt Lake City, UT 84112-9023

REPORT DATE: September 2014

TYPE OF REPORT: Annual

PREPARED FOR: U.S. Army Medical Research and Materiel Command
Fort Detrick, Maryland 21702-5012

DISTRIBUTION STATEMENT: Approved for Public Release;
Distribution Unlimited

The views, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy or decision unless so designated by other documentation.

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE September 2014		2. REPORT TYPE Annual		3. DATES COVERED 29 Aug 2013 – 28 Aug 2014	
4. TITLE AND SUBTITLE Targeted, On-Demand Charge Conversional Nanotherapeutics for Advanced Prostate Cancer				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER W81XWH-13-1-0240	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Xuli Wang, Ph.D. E-Mail: xuli.wang@utah.edu				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) The University of Utah Salt Lake City, UT, 84112				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army Medical Research and Materiel Command Fort Detrick, Maryland 21702-5012				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION / AVAILABILITY STATEMENT Approved for Public Release; Distribution Unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT In this project, we have proposed to design and test an innovative nanotherapeutic system to attack prostate cancer occurred in skeletal tissue. The proposed targeted, bio-responsive nanotherapeutics are based on peptide-functionalized diblock copolymers of poly(ethylene glycol) and poly(trimethenecarbonate) (PEG-PTMC) as the drug carrier, by using docetaxel as the therapeutic agent. During the first reporting period, copolymers with predetermined terminal functionality, molecular weights and chemical compositions have been synthesized, and the physicochemical properties of nanotherapeutics including drug loading capacity and drug release profile have been investigated. The peptide functionalized nanotherapeutics possess high HA binding affinity, indicating their good bone-targeting capacity. For the future study, in vivo bone uptake and retention of the nanotherapeutics in mice will be performed. The nanotherapeutics also will be investigated in cultured prostate cells to determine biological properties in terms of cathepsin K-triggered cellular uptake and anti-tumor efficacy. Finally, the proposed nanotherapeutics will be tested in mice with prostate cancer induced bone metastases.					
15. SUBJECT TERMS Prostate cancer, bone metastasis, bone-targeting, drug delivery system					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT	b. ABSTRACT	c. THIS PAGE			USAMRMC
U	U	U	UU	23	19b. TELEPHONE NUMBER (include area code)

Table of Contents

	<u>Page</u>
1. Introduction.....	4
2. Keywords.....	4
3. Accomplishments.....	4
4. Impact.....	9
5. Changes/Problems.....	9
6. Products.....	9
7. Participants & Other Collaborating Organizations.....	10
8. Special Reporting Requirements.....	11
9. Appendices.....	11

1. **INTRODUCTION:**

Advanced prostate cancer frequently leads to skeletal complications that are very difficult to treat and result in pain, bone fractures, nerve compression, morbidity, and often mortality, and it is considered to be an incurable disease. Current therapeutic options are usually palliative in nature and there is a clear need for better treatment options for bone metastatic prostate cancers. This proposal addresses such an important public health need. Specifically, this project proposes a novel osteotropic, bio-responsive, and prostate-specific drug delivery system for advanced prostate cancer induced bone metastases. The proposed nanotherapeutic system using a multilevel targeting strategy could lead to a more effective approach to attack prostate cancers. The nanotherapeutics possess favorable pharmacological features to improve bioavailability. Additionally, such a therapeutic strategy to deliver therapeutic agents into metastatic bone microenvironments may lead to a potential synergistic effect and improve overall therapeutic efficacy.

2. **KEYWORDS:** Prostate cancer, bone metastasis, bone-targeting, drug delivery system

3. **ACCOMPLISHMENTS:**

What were the major goals of the project?

In this application, we intend to design and test an innovative nanotherapeutic system to attack prostate cancer occurred in skeletal tissue. The proposed targeted, bio-responsive nanotherapeutics are based on a peptide functionalized diblock copolymers of poly(ethylene glycol) and poly(trimethenecarbonate) (PEG-PTMC) as the drug carrier, by using docetaxel as the therapeutic agent. Copolymers with predetermined terminal functionality, molecular weights and chemical compositions will be synthesized to fine-tune the amphiphilicity, solubility and drug loading capacity of the carriers. We will evaluate the physicochemical properties of nanotherapeutics including size, drug loading capacity, and drug release profile. We will also perform studies to determine *in vivo* HA binding affinity, *in vivo* bone uptake and retention of the nanotherapeutics. The nanotherapeutics will be extensively investigated in cultured prostate cells to determine biological properties in terms of CTSK-triggered cellular uptake and anti-tumor efficacy. Finally, the proposed nanotherapeutics will be tested in mice with prostate cancer induced bone metastases.

To accomplish the objectives of the proposed research, the following tasks will be achieved:

Task 1: Synthesize and characterize the nanotherapeutic constructs.


Task 2: Determine *in vitro* HA binding affinity, *in vivo* bone uptake and retention of the Asp8-containing nanoparticles.

Task 3: Investigate and evaluate biological activities of the docetaxel-loaded nanotherapeutics in terms of cellular uptake and tumor inhibition in cultured prostate cancer cells.

Task 4: Therapeutic evaluation of the proposed nanotherapeutics and appropriate controls in mice with prostate cancer induced bone metastases.

What was accomplished under these goals?

Copolymers with terminus of maleimide functional group as well as their respective control copolymers with non-functional methyloxyl group, have been obtained via ring-opening polymerization synthetic strategy. The synthetic procedure and reaction condition for preparation of methoxyl- (Scheme 1 (a)) or maleimide- (Scheme 1 (b)) terminated polymers were illustrated in the Figure 1. Typical ^1H NMR spectra for block copolymers with maleimide-terminus or methyloxyl-terminus have been shown in Figure 1.

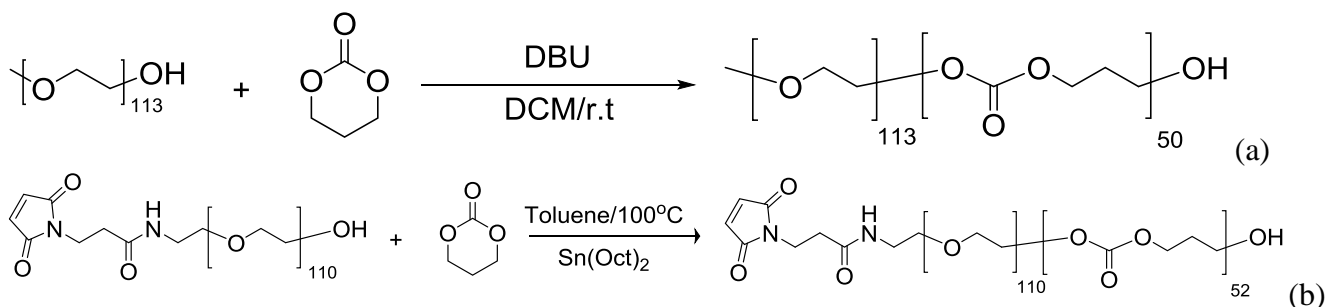

Scheme 1: Synthesis of copolymers with terminus of methoxyl- (a) or maleimide functional group (b)

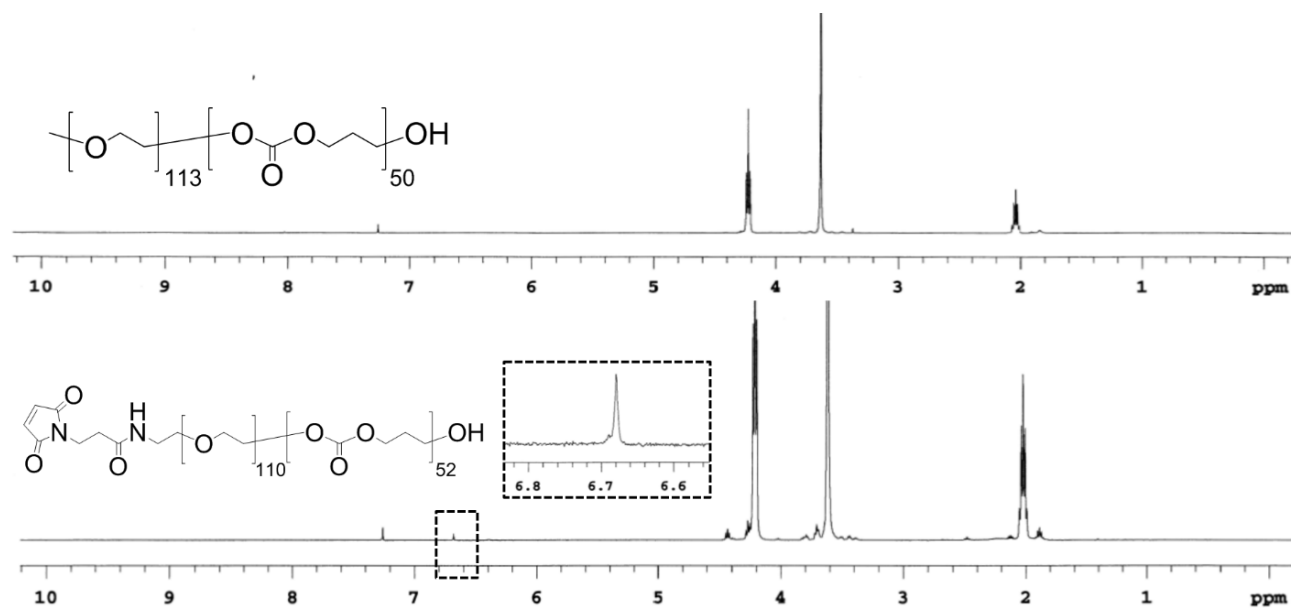


Figure 1. ^1H NMR spectra of block copolymer PEG-PTMC without (upper panel) and with (lower panel) maleimide functional group.

Furthermore, based on Solid-Phase Peptide Synthesis (SPPS) strategy, a functional peptide with sequence of CKGHPGGPQAsp8 has been successfully obtained. Briefly, the functional peptide was synthesized by using Rink amide resin solid support and HBTU/HOBt as coupling reagents. Coupling efficiencies were monitored by the Kaiser ninhydrin test. The peptide was cleaved from the resin by treatment with TFA/EDT/H₂O/TIBS (94/2.5/2.5/1) mixture as scavengers. The crude was precipitated with cold ethyl ether and purified by preparative RP-HPLC. The purity of peptide was checked by analytical RP-HPLC. Typical HPLC profile for the peptide has been shown in Figure 2. Its molecular weight was confirmed by mass spectroscopy, as shown in Figure 3.

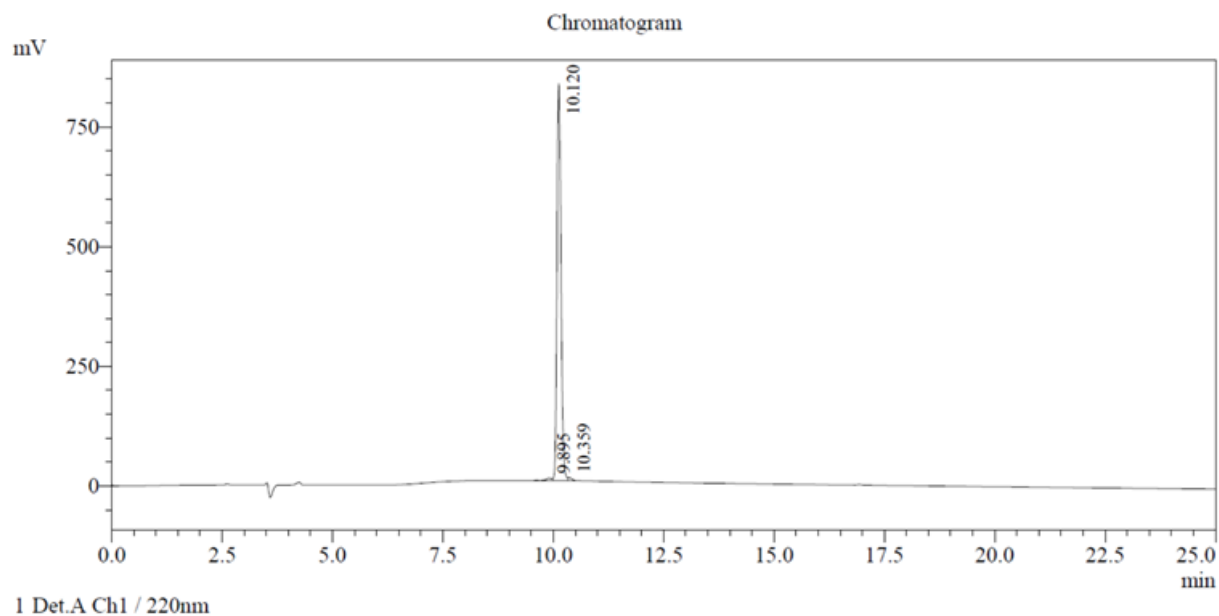


Figure 2. HPLC profile of CKGHGGPQAsp₈ demonstrates its high purity (>98%)

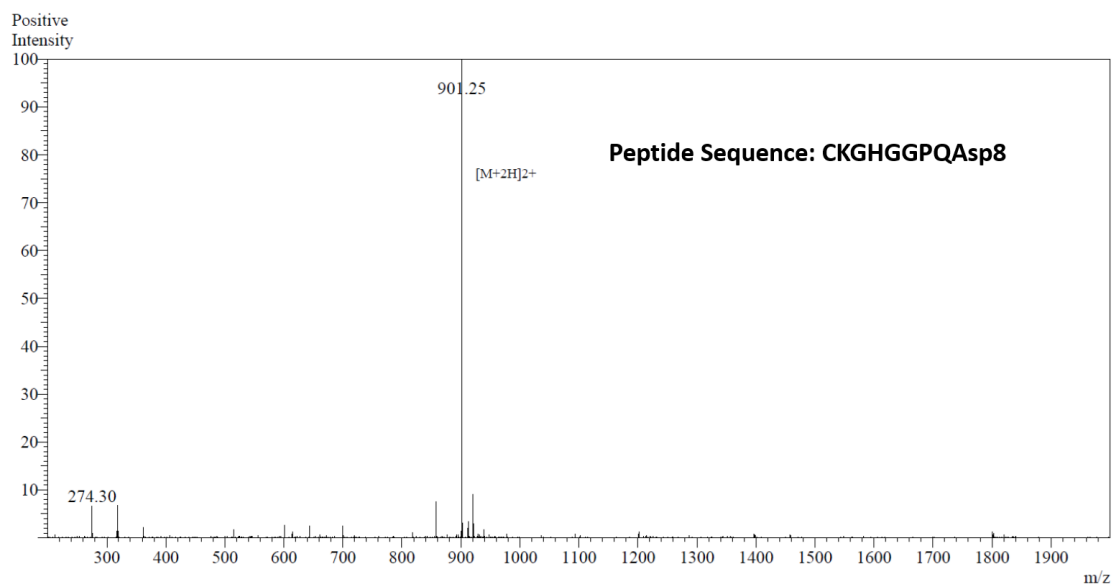


Figure 3. Molecular weight characterization of peptide (CKGHGGPQAsp₈).

Ligand DUPA was synthesized according to Scheme 2. Briefly, to a dried three-neck flask was added L-glutamate di-tert-butyl ester hydrochloride (1.2 g) and 100 mL of DCM under nitrogen atmosphere. After the solution was cooled to -65 °C, triphosgene (400 mg) and 1.25 mL of triethylamine were added. Then this solution was stirred for 6 h and temperature gradually raised from -65 °C to 4 °C under the protection of nitrogen. The solution was re-cooled to -65 °C before adding a solution of L-Glu(OBn)-OtBu (1.5 g) and triethylamine (1.5 mL) in DCM (50 mL). The reaction mixture was allowed to increase to room temperature over a period of 2 h and stirred at room temperature overnight. The reaction was quenched with HCl, and the organic layer was washed with water, brine and dried over anhydrous sodium

sulfate. The crude product was purified using flash chromatography to obtain product as colorless oil. This compound (1 g, 1.73 mmol) was dissolved in 30 mL of DCM, then 10% Pd/C (200 mg) was added into this solution. The reaction mixture was hydrogenated at 1 atm for 24 h at room temperature. Pd/C was filtered through a Celite pad and washed with DCM. The crude product was purified by using flash chromatography to obtain the desired product as white solid.

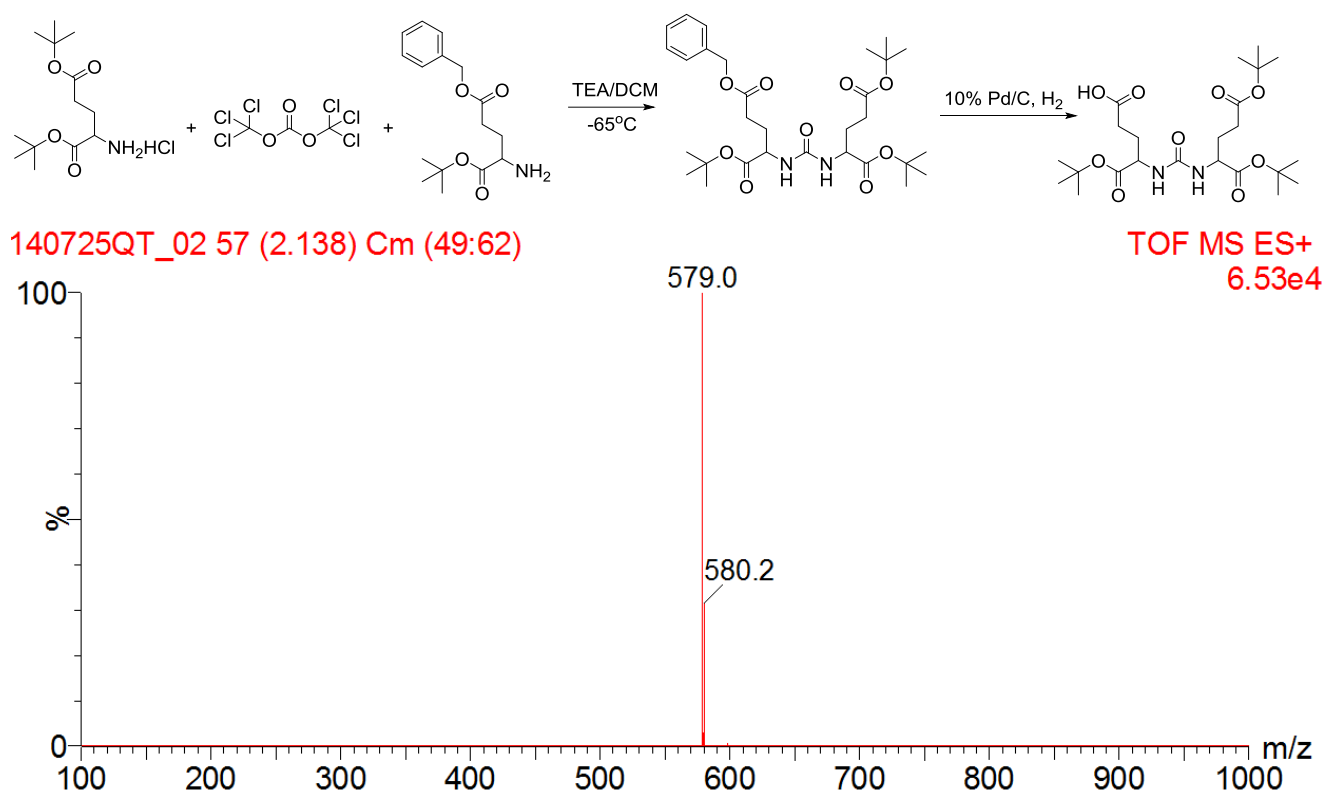


Figure 4: Synthesis and molecular weight characterization of DUPA ligand

Conjugation DUPA onto peptide was performed using EDC/NHS conjugation strategy. The availability of thiol group is critical for subsequent functionalization of nanotherapeutics yet thiol group is well-known to be very sensitive to air oxidation. Hence, CK(DUPA)GHPGGPQAsp8 was freshly activated with EDC/NHS followed by TFA deprotection and the intermediate was used directly without further purification for subsequent reaction as extensive purification procedure may cause thiol oxidation. Fortunately, small molecular weight intermediate can be easily removed by later on dialysis procedure. Tri-block copolymers were synthesized through thiol-maleimide reaction. The conjugation of peptide into PEG-PTMC block copolymers was straightforward. For example, after a brief treatment of the peptide with tris(2-carboxyethyl) phosphine (TCEP) in phosphate buffered saline (PBS) at pH = 7.4, the peptide solution was added dropwise into Mal-PEG-block-PTMC solution in dimethyl sulfoxide, and reaction was allowed to continue overnight at 4°C. Peptide-b-PEG-block-PTMC tri-block copolymer was purified by dialysis (4°C), followed by ultrafiltration (MWCO = 10 K), and finally dried by lyophilization. Successful conjugation was verified by complete disappearance of the maleimide signal at $\sigma = 6.74$ ppm in ¹H NMR spectrum.

To better understand the potential of Pep-*b*-PEG-*b*-PTMC as a drug carrier, docetaxel (DTX) was used as a model drug to determine drug loading and release properties. DTX was encapsulated into the micelles of Pep-*b*-PEG-*b*-PTMC by a dialysis method and drug loading capacity was determined by HPLC. Pep-*b*-PEG-*b*-PTMC showed 3.16 ± 0.33 % and 31.6 ± 3.3 % for loading content and loading efficiency, respectively. As determined by dynamic light scattering, polymer micelles resulted from Pep-*b*-PEG-*b*-PTMC before DTX loading possess particle size of 47 ± 2.5 nm in diameter. Their size increased to 65 ± 2.6 nm in diameter after DTX loading into micelles. Drug release profile in PBS buffer at pH 7.4 suggested that DTX-loaded micelles exhibited a moderately rapid release in the first stage (approximately 15 % for the first 2 hours) followed by a sustained release period. The sustained DTX release could be attributed to the hydrophobic interaction of drug molecules with the hydrophobic core of the polymeric micelles.

The strong binding ability of Pep-*b*-PEG-*b*-PTMC micelles to hydroxyapatite (HA), commonly used as a model mineral to mimic bone tissue mineral, was examined to preliminarily evaluate the contribution of peptide functionality to the bone-seeking efficacy. Cy5.5 was encapsulated into the micellar cores by the dialysis method thus to quantitatively determine the binding affinities of the nanomicelles with and without peptide functionality, respectively. After incubation for 30 min, approximately 86.2 ± 1.6 % of the CK(DUPA)GHPGGPQAsp₈ modified NPs were rapidly bound to HA. In marked contrast, less than 10 % of MPEG-*b*-PTMC micelles or free Cy5.5 were bound to HA, indicating minimal nonspecific binding to HA by the MPEG-*b*-PTMC micelles absent of peptide functionality. Those results correlated well with the reported findings that modification with osteotropic Asp₈ would dramatically facilitate the specific binding towards HA-rich bone tissue.

In summary, during the first reporting period, we have been focusing on the synthesis and characterization of drug carriers for bone-targeted, bio-responsive nanotherapeutics for advanced prostate cancer therapy, and the progress in the first year of this project was good. It has created a strong foundation for more rapid progress in the subsequent years to test our nanotherapeutic constructs. As planned, we will investigate and evaluate such constructs in cultured prostate cancer cells as well as in a prostate cancer animal model for the next two years.

What opportunities for training and professional development has the project provided?

"Nothing to Report."

How were the results disseminated to communities of interest?

"Nothing to Report."

What do you plan to do during the next reporting period to accomplish the goals?

The progress in the first year of this project has established a strong platform for more rapid progress in the subsequent years to test our nanotherapeutic constructs. For the next reporting period, we will start to investigate and evaluate biological activities of the docetaxel-loaded nanotherapeutics in terms of cellular uptake and tumor inhibition in cultured prostate cancer cells. We also will initiate *in vivo* studies. Specifically, we will determine bone uptake and retention of the proposed nanotherapeutics in mice. Meanwhile, we will start to establish animal model of prostate cancer induced bone metastatic animal model for future *in vivo* tumor inhibition studies.

4. **IMPACT:**

What was the impact on the development of the principal discipline(s) of the project?

"Nothing to Report."

What was the impact on other disciplines?

"Nothing to Report."

What was the impact on technology transfer?

"Nothing to Report."

What was the impact on society beyond science and technology?

"Nothing to Report."

5. **CHANGES/PROBLEMS:**

"Nothing to Report"

Changes in approach and reasons for change

"Nothing to Report"

Actual or anticipated problems or delays and actions or plans to resolve them

"Nothing to Report"

Changes that had a significant impact on expenditures

"Nothing to Report"

Significant changes in use or care of human subjects, vertebrate animals, biohazards, and/or select agents

"Nothing to Report"

6. **PRODUCTS:**

Mnauscript:

Xuli Wang, Ye Yang, Huizhen Jia, Wanjian Jia, Scott Miller, Beth Bowman, Jun Feng and Fenghuang Zhan, Peptide decoration of nanovehicles to achieve active targeting and pathology-responsive cellular uptake for bone metastasis chemotherapy, *Biomaterials Science*, **2014**, 2, 961-971

7. PARTICIPANTS & OTHER COLLABORATING ORGANIZATIONS

What individuals have worked on the project?

Name:	Xuli Wang, Ph.D.
Project Role:	Principal Investigator
Nearest person month worked:	4
Contribution to Project:	Responsible for the overall management of the project. Dr. Wang has also involved in chemical synthesis for this project.
Funding Support:	This award and support from NCI
Name:	Mary Beth Bowman
Project Role:	Technician
Nearest person month worked:	3
Contribution to Project:	Ms. Bowman has performed work in the area of investigation and evaluation of nanotherapeutics.
Funding Support:	This award.
Name:	Le Zhan
Project Role:	Technician
Nearest person month worked:	6
Contribution to Project:	Ms. Zhan has performed work in the area of investigation and evaluation of nanotherapeutics.
Funding Support:	This award.
Name:	Tao Liu
Project Role:	Graduate Student
Nearest person month worked:	5
Contribution to Project:	Mr. Liu has performed work in the area of chemical synthesis and characterization of nanotherapeutics.
Funding Support:	NCI

Has there been a change in the active other support of the PD/PI(s) or senior/key personnel since the last reporting period?

"Nothing to Report."

What other organizations were involved as partners?

"Nothing to Report."

8. **SPECIAL REPORTING REQUIREMENTS**


N.A.

9. **APPENDICES:**

A manuscript has been attached.

Biomaterials Science

www.rsc.org/biomaterialsscience

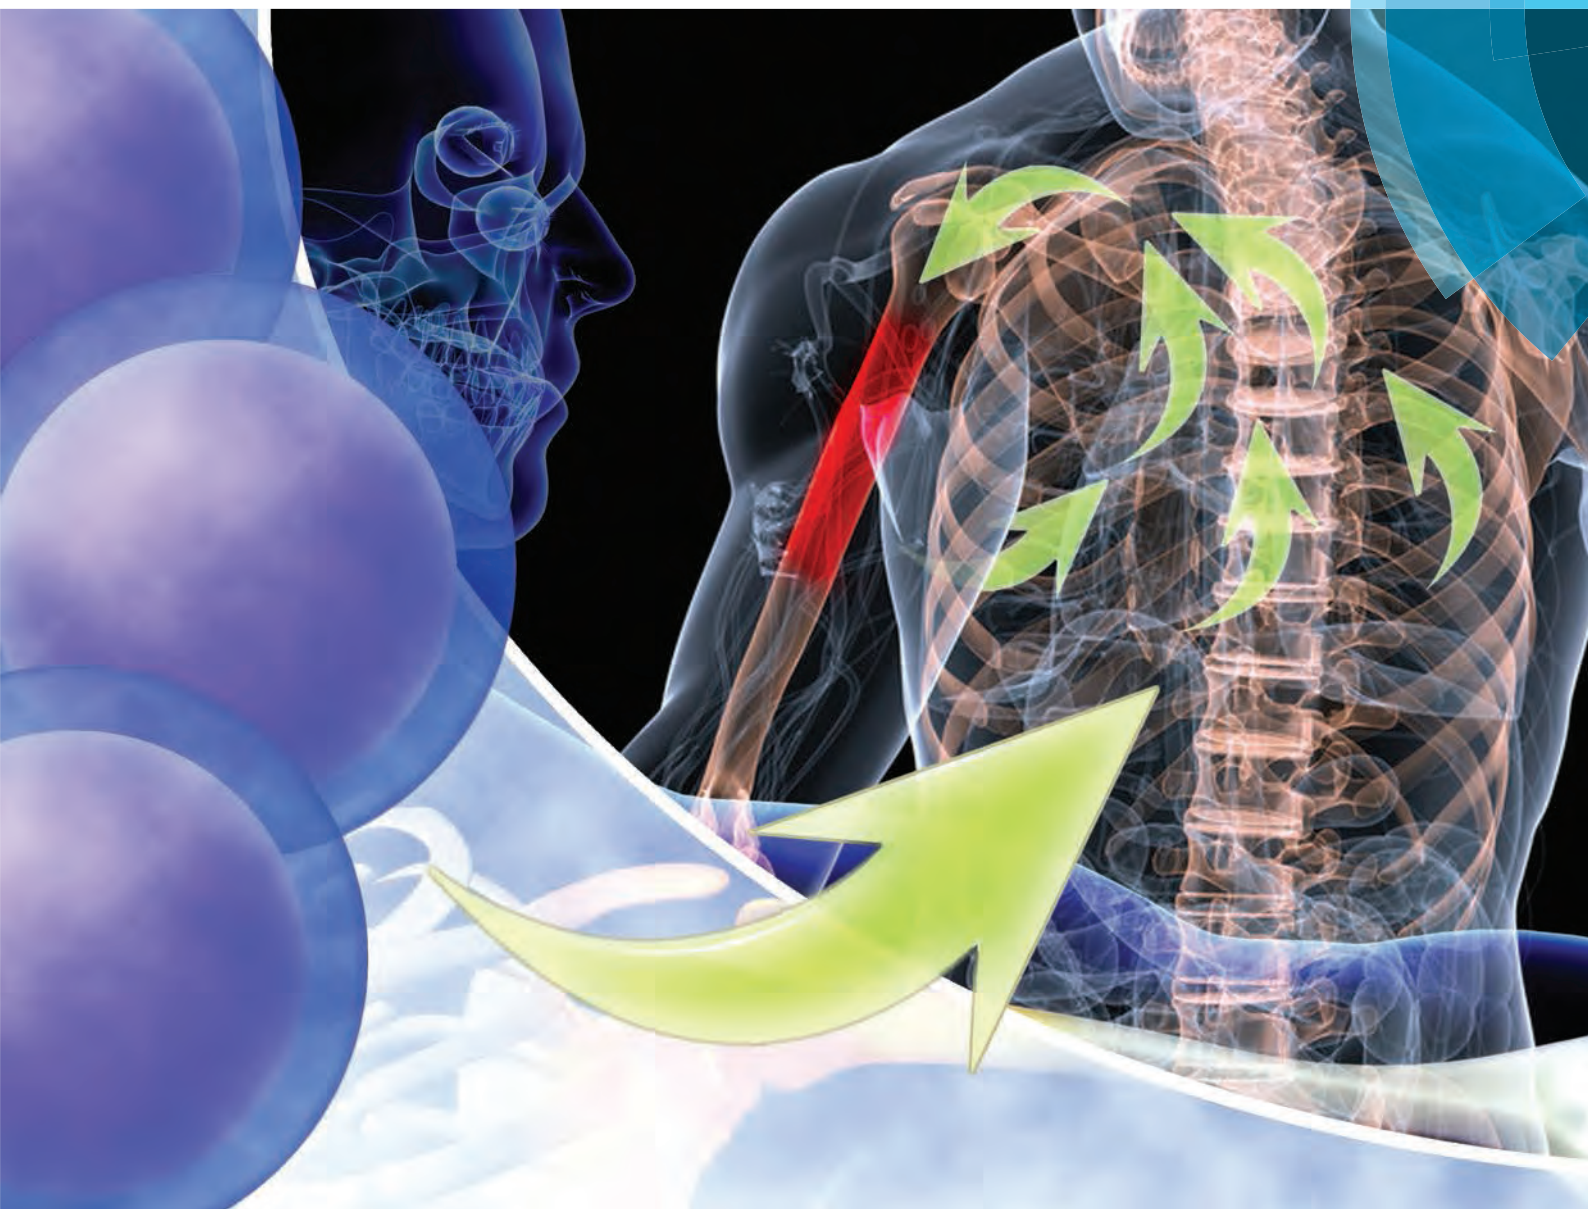

ISSN 2047-4830



PAPER

Xuli Wang, Jun Feng, Fenghuang Zhan *et al.*
Peptide decoration of nanovehicles to achieve active targeting and
pathology-responsive cellular uptake for bone metastasis chemotherapy



Cite this: *Biomater. Sci.*, 2014, **2**, 961

Peptide decoration of nanovehicles to achieve active targeting and pathology-responsive cellular uptake for bone metastasis chemotherapy†

Xuli Wang,^{*,‡,a} Ye Yang,^{‡,b} Huizhen Jia,^c Wanjian Jia,^a Scott Miller,^a Beth Bowman,^a Jun Feng^{*,c} and Fenghuang Zhan^{*,b}

To improve bone metastasis chemotherapy, a peptide-conjugated diblock copolymer consisting of a chimeric peptide, poly(ethylene glycol) and poly(trimethylene carbonate) (Pep-*b*-PEG-*b*-PTMC) is fabricated as a drug carrier capable of bone-seeking as well as pathology-responsive charge reversal to ensure effective cellular uptake at the lesion sites. The chimeric peptide CKGHPGGPQAsp₈ consists of an osteotropic anionic Asp₈, a cathepsin K (CTSK)-cleavable substrate (HPGGPQ) and a cationic residue tethered to the polymer chain. Pep-*b*-PEG-*b*-PTMC can spontaneously self-assemble into negatively charged nanomicelles (~75 nm). As to the model drug of doxorubicin, Pep-*b*-PEG-*b*-PTMC shows 30.0 ± 1% and 90.1 ± 2% for the loading content and loading efficiency, respectively. High bone binding capability is demonstrated with 66% of Pep-*b*-PEG-*b*-PTMC micelles were able to bind to hydroxyl apatite, whereas less than 15% of Pep-free micelles were bound to hydroxyl apatite. The nanomicelles exhibit a negative-to-positive charge conversion from -18.5 ± 1.9 mV to 15.2 ± 1.8 mV upon exposure to CTSK, an enzyme overexpressed in bone metastatic microenvironments. Such a pathology-responsive transition would lead to remarkably enhanced cellular uptake of the nanomicelles upon reaching lesion sites, thus improving the drug efficacy as verified by the *in vitro* cytotoxicity assay and the *in vivo* study with the myeloma-bearing 5TGM1 mice model.

Received 19th January 2014,

Accepted 11th March 2014

DOI: 10.1039/c4bm00020j

www.rsc.org/biomaterialsscience

1. Introduction

Most patients with cancer die not because of the tumor in the primary site, but rather because it spread to other sites of which the bone is the most common organ to be affected.^{1,2} Patients with bone metastases generally cannot be treated curatively, *e.g.*, only 20% of patients with breast cancer remain alive for five years after the diagnosis of bone metastases; more than 550 000 people die annually with bone metastases.^{1,3} Effective chemotherapy of bone metastases has therefore remained an urgent challenge for cancer treatments.⁴

The surface decoration of drug nanovehicles (NVs) with bone-targeting moieties is among the most used strategies to improve the chemotherapy against bone metastases.⁵ Given

the remarkable feature of skeletal tissue rich in apatite (Ca₁₀(PO₄)₆), many anionic agents with high apatite binding affinity including bisphosphonates (BPs) and oligopeptides (Asp₆, Asp₈ and Glu₈) have been purposely incorporated into NVs for the sake of bone-seeking action.^{5–7} However, the treatment efficacies achieved by those bone-targeting NVs are still far from satisfactory; some of them were even less efficacious than the unmodified counterparts. The marked deviation from the expectation is thought to be associated with the dilemma that the attachment of anionic agents to NVs inevitably restricts cellular translocation due to the charge repulsion by the cell membranes.^{4–6} In turn it is difficult for the drugs loaded into NVs to enter cancerous cells to elicit therapeutic action. In contrast, despite the easy intracellular internalization, the applications of positively charged NVs suffer a lot from rapid *in vivo* clearance and non-specific uptake by healthy tissues resulting from the strong interaction with oppositely charged blood components and the cell membranes. Taking those into account, the solution to bone-targeted chemotherapy may eventually rely on the rational design of anionic bone-seeking NVs which are simultaneously capable of undergoing negative-to-positive charge transition that mostly occurs in bone metastatic sites.


^aDivision of Radiobiology, School of Medicine, University of Utah, 729 Arapleen Drive, Rm 2334, Salt Lake City, 84108, USA. E-mail: xuli.wang@utah.edu

^bDepartment of Internal Medicine, Division of Hematology, Oncology, and Blood & Marrow Transplant, University of Iowa, Iowa City, IA 52242, USA. E-mail: fenghuang-zhan@uiowa.edu

^cKey Laboratory of Biomedical Polymers of Ministry of Education & Department of Chemistry, Wuhan University, Wuhan 430072, China. E-mail: fengjun@whu.edu.cn

†Electronic supplementary information (ESI) available. See DOI: 10.1039/c4bm00020j

‡These authors contributed equally.

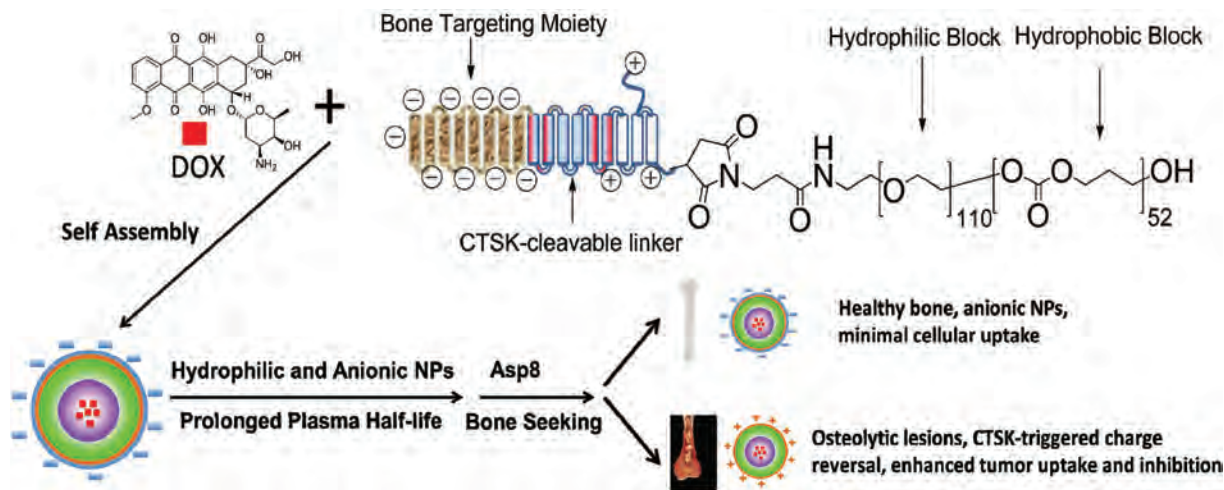

Scheme 1 Schematic illustration of nanotherapeutic formation and its mechanism of action *in vivo* for bone metastasis treatment.

One notable physicochemical feature of bone metastases is the predominant over-expression of several proteases including matrix metalloproteinase, urokinase plasminogen activator, and cathepsins (cathepsins K, L, and B).⁸ In particular, the development of cancer metastases in bones is found to be highly correlated with the expression level of the acid-activated cathepsin K enzyme (CTSK). The bone metastatic lesions express even dramatically higher level of CTSK compared to primary tumor and soft tissue metastases.⁹ The strong dependence of bone metastases on the CTSK level makes CTSK able to serve as a prognostic indicator for the diagnosis of bone metastases and as a therapeutic target for disease treatments.^{10–12} This pathology-dependent feature of CTSK overexpression evokes our interest to exploit CTSK as the biological stimulus to locally trigger the charge reversal of anionic bone-seeking NVs upon reaching bone metastatic sites.^{13–16}

We have herein designed a bone-seeking, CTSK-responsive charge-reversal NV system for efficient chemotherapy of bone metastases. This delivery system was constructed on the core-shell nanomicelles self-assembled from a triblock copolymer (Pep-*b*-PEG-*b*-PTMC) composed of a peptide segment with the sequence CKGHPGGPQAsp₈, poly(ethylene glycol) and poly(trimethylene carbonate). The chimeric peptide segment consisted of three main functional modules: the anionic Asp₈ is responsible for the direction and accumulation of NVs into the skeletal tissues, the HPGGPQ serves as the CTSK-cleavable substrate,⁸ and the remaining cationic residue is chemically conjugated to the PEG shell of the micelles. In this way, the combination of the targeting function of Asp₈ and the stealth effect of the PEG shell would help the drug-loaded Pep-*b*-PEG-*b*-PTMC nanomicelles prolong the circulation time and minimize the undesirable cellular uptake by healthy cells. Of special note is that the bone metastatic microenvironment featured with CTSK overexpression would locally stimulate the enzymatic cleavage of HPGGPQ moieties, leaving the cationic peptide residue on the shell periphery. This pathology-responsive charge reversal transition is

expected to largely contribute to the selectively efficient internalization of nanomicelles into the neighboring cancerous cells (Scheme 1), thus improving the therapeutic efficacy. In principle, this strategy of bone-seeking, pathology-responsive charge-reversal NVs may be also applicable to other malignant diseases of skeletal tissue if the development of those diseases involves overexpression of certain enzymes. To verify our hypothesis, an anticancer drug DOX was used as the drug model and the *in vitro* and *in vivo* properties of the Pep-*b*-PEG-*b*-PTMC nanomicelles were comparatively explored under the CTSK-rich and CTSK-absent conditions.

2. Experimental section

2.1. Materials

Monomethyl terminated polyethylene glycol monoamine (MeO-PEG₁₁₃-OH, $M_w = 5000$ Da) was purchased from Sigma-Aldrich. It was dried by azeodistillation of anhydrous benzene prior to use. Heterofunctional PEG with monomaleimide and monohydroxyl terminus (Mal-PEG₁₁₀-OH, $M_w = 5000$ Da) was purchased from Laysan Bio (Arab, AL) and dried under high vacuum. Trimethylene carbonate (TMC) was prepared as previously described.¹⁷ It was recrystallized from a THF-ether mixture, and further purified *via* sublimation prior to use. 1,8-Diazabicyclo[5.4.0]undec-7-ene (DBU) was distilled from CaH₂ under dry N₂ prior to use. The *N*-(3,5-trifluoromethyl)phenyl-*N*-cyclohexylthiourea (TU) catalyst was prepared as described elsewhere.¹⁸ Stannous octoate (Sn(Oct)₂, Sigma) was purified according to a method described in the literature.¹⁹ Anhydrous solvents were purchased from Sigma-Aldrich and stored over molecular sieves (4 Å). Doxorubicin was purchased from Selleck Inc. (Houston, TX). Cy5.5 was purchased from Lumiprobe (Russia). Cathepsin K was purchased from EMD Biosciences. Hydroxyapatite (HA) was purchased from Bio-Rad (Bio-Gel HTP, DNA grade; Hercules, CA). 1-Hydroxybenzotriazole (HOBt), *O*-benzotriazole-*N,N,N',N'*-tetramethyl-uronium-

hexafluoro-phosphate (HBTU), Rink amide resin, NovaSyn TGT alcohol resin and all of the amino acids for solid phase peptide synthesis were purchased from Novabiochem (CA). All other chemical reagents were available commercially and used as received unless otherwise noted.

2.2. Peptide synthesis

ISOLUTE column reservoirs (Charlottesville, VA) were used for the solid phase synthesis. The functional peptide with the sequence of CKGHPGGPQAsp₈ was synthesized by a standard solid phase peptide synthesis (SPPS) procedure by using the Rink amide resin solid support and HBTU/HOBt as coupling reagents. Coupling efficiencies were monitored by the Kaiser ninhydrin test. The peptide was cleaved from the resin by treatment with the TFA-EDT-H₂O-TIBS (94/2.5/2.5/1) mixture as a scavenger. The crude was precipitated with cold ethyl ether and purified by preparative RP-HPLC. The purity of the peptide was checked by analytical RP-HPLC and the molecular weight was confirmed by MALDI-TOF mass spectrometry, MS (*m/z*, [*M*]⁺): 1800.68 (calculated for C₆₈H₉₇N₂₁O₃₅S); 1800.54 (found).

2.3. Synthesis of the MPEG-*b*-PTMC di-block copolymer (MPEG-*b*-PTMC)

HO-PEG₁₁₃-OMe (5 g, 1 mmol), TMC (5.1 g, 50 mmol) and TU (380.6 mg, 2.5 mmol, 5 mol% of TMC monomer) were dissolved in 25 mL dichloromethane (DCM), and then DBU (380.6 mg, 2.5 mmol, 5 mol% of TMC monomer) was added. The reaction was performed under a N₂ atmosphere for 24 hours. The reaction mixture was concentrated under a reduced pressure and the product was obtained by precipitation in ether. The residue was re-dissolved in a minimal amount of DCM and then poured into cold ether to precipitate the product; total yield: 8.6 g (85.2%).

2.4. Synthesis of the maleimide-terminated PEG-*b*-PTMC polymer (Mal-PEG-*b*-PTMC)

Mal-PEG₁₁₀-*b*-PTMC₅₂ was synthesized by ring-opening polymerization using Mal-PEG₁₁₀-OH (0.5 g) as the initiator, Sn(Oct)₂ as the catalyst and anhydrous toluene as the solvent. The reaction was performed at 100 °C under a N₂ atmosphere for 16 hours. The reaction mixture was concentrated under a reduced pressure and the product was obtained by precipitation in ether. The residue was re-dissolved in a minimal amount of THF and then poured into cold ether to precipitate the product. Yield: 0.72 g (71.3%).

2.5. Synthesis of the peptide-*b*-PEG-*b*-PTMC copolymer (peptide-*b*-PEG-*b*-PTMC)

Peptide (CKGHPGGPQAsp₈, 50 mg, 27.8 μmol) was dissolved in PBS buffer (pH = 7.2) and treated with tris(2-carboxyethyl) phosphine (TCEP, 40 μmol) for 2 hours under a N₂ atmosphere. After that, 213 mg of Mal-PEG-*b*-PTMC in 5 mL of dimethylacetamide (DMAc) was added. The reaction was performed at room temperature overnight. The reaction mixture was then subject to dialysis against water (MWCO = 6–8 kDa,

Spectrumlabs) at 4 °C for 24 hours. The solution was further purified using Microsep™ Centrifugal Devices with the Omega™ Membrane (MWCO = 10 kDa, Pall Life Sciences). The final product was recovered and dried by lyophilization. Yield: 151 mg (57.5%).

2.6. NMR characterization

The MERCURY 400 MHz spectrometer was used for recording ¹H NMR spectra to determine the structure and composition of the block copolymers. Deuterium oxide (D₂O), deuterated chloroform (CDCl₃) and dimethyl sulfoxide (DMSO-*d*₆) were used as the solvents as noted for NMR measurements.

2.7. Determination of critical micelle concentration (CMC)

Critical micelle concentrations of the copolymers were estimated by a fluorescence spectroscopy method using pyrene as the fluorescence probe.²⁰ A predetermined amount of pyrene solution in acetone was added into a series of volumetric flasks, and the acetone was then evaporated completely. A series of copolymer solutions of different concentrations ranging from 1.0 × 10^{−5} to 1.0 mg mL^{−1} were added to the bottles, whereas the concentration of pyrene in each flask was fixed at a constant value (6.0 × 10^{−7} mol L^{−1}). The excitation spectra were recorded at 20 °C on a Shimadzu RF-5301PC spectrofluorophotometer with the detection wavelength at 390 nm and a slit width of 3 nm. The intensity ratio of the bands at 340 and 338 nm (*I*₃₄₀/*I*₃₃₈) as a function of the logarithm of the concentration of copolymers was plotted and the CMC value was taken as the intersection of the tangents to the horizontal line of the intensity ratio with relatively constant values and the diagonal line with rapid increased intensity ratio.

2.8. Preparation of self-assembled nanoparticles

2.8.1. Preparation of blank nanoparticles. Blank micelles were prepared by a dialysis method. Briefly, the block copolymer (10 mg) was dissolved in 1 mL of DMSO and stirred for 10 min at room temperature. Then, 5 mL of double distilled water was added dropwise into the polymer solution under stirring. After 30 min, the solution was transferred into a dialysis membrane tubing (MWCO = 6–8 kDa, Spectrumlabs) and dialyzed for 24 h against distilled water to remove the organic solvent. The solution was recovered and lyophilized to afford blank nanoparticles.

2.8.2. Preparation of fluorescence-labeled nanoparticles. In order to track nanoparticles, fluorescence-labeled nanoparticles were prepared using Cy5.5 as a fluorescent tracer. Cy5.5-labeled nanoparticles were similarly prepared following the above-described dialysis method.

2.8.3. Preparation of DOX-loaded NVs. Unless otherwise noted, all procedures for preparation and handling of DOX-loaded NVs were performed in the dark. DOX-loaded micelles were prepared similarly to the blank micelles. Briefly, 10 mg of each polymer was dissolved in 1 mL of DMSO, followed by adding a predetermined amount of DOX-HCl and two molar equivalents of triethylamine (TEA) and stirred at room temp-

erature for 1 h. Then, 5 mL of double distilled water was added dropwise. After being stirred for an additional 1 h, the solution was dialyzed (MWCO = 6–8 kDa, Spectrumlabs) against water for 24 h. Drug-loaded NVs were dried *via* lyophilization.

2.9. Determination of drug loading capacity

The drug loading content was determined spectrophotometrically by measuring the absorption of the lyophilized sample which was dissolved in DMSO at a wavelength of 482 nm. The absorbance of DOX in nanoparticles was measured to determine the drug content in the solution using an established calibration curve with a known concentration of free DOX. The percentages of DLC (drug loading content) and DLE (drug loading efficiency) were calculated according to the following equations:

$$\text{DLC (\%)} = \frac{\text{amount of DOX in micelle}}{\text{amount of DOX-loaded micelles}} \times 100\%$$

$$\text{DLE (\%)} = \frac{\text{amount of DOX in micelle}}{\text{amount of DOX used for nanomicelle preparation}} \times 100\%$$

2.10. Drug release profile

Drug release experiments were performed in a buffer with a fixed ionic strength at 150 mM using saline. Appropriate pH was maintained with phosphate buffer (10 mM, pH 5.5 or 7.4) solutions. DOX-loaded micelle solution was diluted to 1 mg mL⁻¹, and transferred into a dialysis membrane tubing (Spectra/Por, Float-A-Lyzer G2, MWCO = 8–10 kDa). The tubing was immersed in 100 mL of the release medium and kept in a horizontal laboratory shaker maintaining a constant temperature (37 °C) and stirring (100 rpm). Samples were periodically removed and replaced with the same volume of fresh medium. The amount of released DOX was analyzed with a spectrophotometer at 482 nm. The drug release studies were performed in triplicate for each of the samples.

2.11. Dynamic light scattering (DLS)

The hydrodynamic size of the micellar nanoparticles was analyzed using a Brookhaven Instruments BI-200SM system equipped with a 5 mW helium neon laser with a wavelength output of 633 nm. The effective diameter and population distribution were computed from the diffusion coefficient. Measurements were made at 25 °C at an angle of 90°, and each sample was analyzed in triplicate. The micelle solution was filtered using a 0.45 µm membrane filter prior to measurements for all of the experiments.

2.12. Binding affinity of nanoparticles to hydroxyapatite (HA)

The binding affinity of nanoparticles to hydroxyapatite was assessed with free Cy5.5, Cy5.5-loaded nanoparticles or Cy5.5-peptide conjugates.²¹ Cy5.5-peptide conjugates were obtained by direct conjugation of Mal-Cy5.5 (Lumiprobe, Russia) with the peptide *via* thiol-maleimide reaction. The samples were dissolved in phosphate buffered saline (pH 7.4) and then

subjected to incubation with 1 mg of HA powder (HA, Bio-Gel HTP, DNA grade; BIO-RAD, Hercules, CA) in an eppendorf tube at RT. At predetermined time intervals, the incubation was stopped by centrifugation. The UV absorbance of the supernatant was monitored at a wavelength of 660 nm. Each sample was measured in duplicate.

2.13. Cell culture

Myeloma cells (5TGM1 and ARP-1) and breast cancer cells (MCF-7) were cultured in RPMI1640 containing 10% heat-inactivated fetal calf serum (FCS), 4 mM L-glutamine (Gibco), penicillin (100 U mL⁻¹), and streptomycin (100 µg mL⁻¹) at 37 °C in a humidified atmosphere containing 5% CO₂.

2.14. Cell-proliferation assay

The cells were seeded in 96-well plates at 2000 cells per well in 100 µL of complete medium, and incubated at 37 °C in a 5% CO₂ humidified atmosphere, followed by adding DOX-loaded nanoparticles or blank micelles (25 µL) at pre-determined concentrations. Following 48-hour incubation, 12.5 µL of Presto-Blue™ Cell Viability Reagent (Invitrogen) was added to cultured cells. After incubation for an additional 3 h, the absorbance of the solution was measured at 570 and 600 nm using a microplate reader (Molecular Device). The cell number was calculated according to the manufacturer's instructions, and the cell viability was normalized to that of cells without drug treatment.

2.15. Confocal laser scanning microscopy (CLSM)

Confocal laser scanning microscopy was carried out using an Olympus FV-1000 laser scanning microscope operated with the FLUOVIEW software (Olympus, Tokyo, Japan). Images were produced using the lasers sequentially with a 20× objective lens.

2.16. Biological evaluation of CTSK-pretreated nanoparticles

Cathepsin K (EMD Biosciences) was pre-incubated at 37 °C for 5 min to activate the enzyme in the active site, followed by addition of the nanoparticles. The nanoparticles were incubated with cathepsin K (150 nM) at 37 °C in acetate buffer (0.1 M, pH 5.5). The incubation mixture contained 0.15 µM of cathepsin K, 2.5 mM cysteine, and 5 mM EDTA. After CTSK pretreatment for 30 minutes, nanoparticles were recovered *via* ultrafiltration (MWCO = 100 kDa), and then subjected to zeta potential measurements (Malvern Zetasizer 3000), cell incubation for CLSM observation (Olympus FV-1000) or cytotoxicity evaluations. Nanoparticles were pretreated in the cleavage buffer, but in the absence of CTSK were used as the controls.

2.17. *In vivo* test of nanotherapeutics

The preliminary test of DOX-loaded nanotherapeutics was carried out in a 5TGM1 myeloma cell-induced bone metastatic mouse model. Experiments were approved by the Institutional Animal Care and Use Committee of the University of Utah. To establish the mice with bone manifestations of metastatic

cancers, 1×10^6 5TGM1 cells (in 100 μ L PBS) were injected into each mouse through the tail vein and the tumors were allowed to grow for a week. The bone-targeted, CTSK-cleavable nanotherapeutics, as well as the corresponding non-targeted nanotherapeutics (neutral NVs), or free DOX were investigated. The doses of doxorubicin were kept equivalent in different groups. Another group with PBS was used as a negative control. Three C57BL/KaLwRij mice with 5TGM1 inoculations were used for each group. At the time of the experiments, the animal was injected with different therapeutic formulations or controls at a dose of 0.75 mg kg⁻¹ twice a week. The tumor burden in the mice was monitored weekly by ELISA measurements of monoclonal immunoglobulin (Ig) in mouse sera. Survival was evaluated from the day of tumor inoculation until death.

2.18. Statistical analysis

All measurements were conducted in duplicate or triplicate and expressed as mean \pm standard deviation where indicated. Differences between the mean values were analyzed by two-sided Student's *t* test or one-way ANOVA. The Kaplan–Meier curve and log rank test were used for mouse survival. *P* values of <0.05 are considered statistically significant.

3. Results and discussion

A peptide-conjugated diblock copolymer consisting of a peptide, poly(ethylene glycol) and poly(trimethylene carbonate) (Pep-*b*-PEG-*b*-PTMC) has been synthesized for the first time. PEG was used as the hydrophilic block because of its established role to help NVs escape from protein opsonization and macrophage uptake in the reticuloendothelial system. The rationale behind the choice of PTMC as the hydrophobic block was that PTMC can degrade with a relatively slower rate and

have a weak inflammatory effect of degradation compounds, which is a marked advantage over polyesters and particularly attractive to sustained drug delivery application.²²

The synthesis of a peptide-conjugated diblock copolymer of Pep-*b*-PEG-*b*-PTMC was based on the efficient click reaction between the cysteine terminated Pep peptide and the maleimidevinyl terminated Mal-PEG-*b*-PTMC diblock copolymer, as illustrated in Fig. 1. Via the well-established organocatalytic (*i.e.* TU) ring-opening polymerization approach, a non-functional MPEG-*b*-PTMC copolymer could be readily prepared with a defined molecular weight and narrow molecular distribution when using MPEG-OH (M_w = 5000 Da) as the macro-initiator.²³ This strategy was problematic, however, when it came to the synthesis of the maleimide-terminated copolymer of Mal-PEG-*b*-PTMC starting from Mal-PEG-OH. ¹H NMR analysis revealed that the maleimidevinyl protons at σ = 6.74 ppm in the product disappeared. Apparently, the maleimide group might be very labile to super basic conditions, and failed to remain intact during the polymerization process. Alternatively, the Mal-PEG₁₁₀-*b*-PTMC₅₂, in which 52 refers to the repeating units of TMC, was successfully synthesized under mild conditions under Sn(Oct)₂ catalysis (Fig. 1A). ¹H NMR analysis demonstrated that the maleimidevinyl protons at σ = 6.74 ppm in the product remained available after polymerization (Fig. 2). The copolymer composition and number-averaged molecular weight of Mal-PEG₁₁₀-*b*-PTMC₅₂ were determined from the integral ratio of PTMC protons at σ = 4.21 ppm *versus* that of the PEG proton at σ = 3.64 ppm. For comparison purposes, the peptide-free methoxy-terminated MPEG₁₁₃-*b*-PTMC₅₀ was also prepared.

Next, we synthesized the functional peptide with a specially designed sequence of CKGHPPGGPQAsp₈ based on the solid phase peptide synthesis (SPPS) technique (Fig. 1B). The purity (98%) and molecular weight (calculated: 1800.64, found: 1800.54) of the target peptide were confirmed by high-perform-

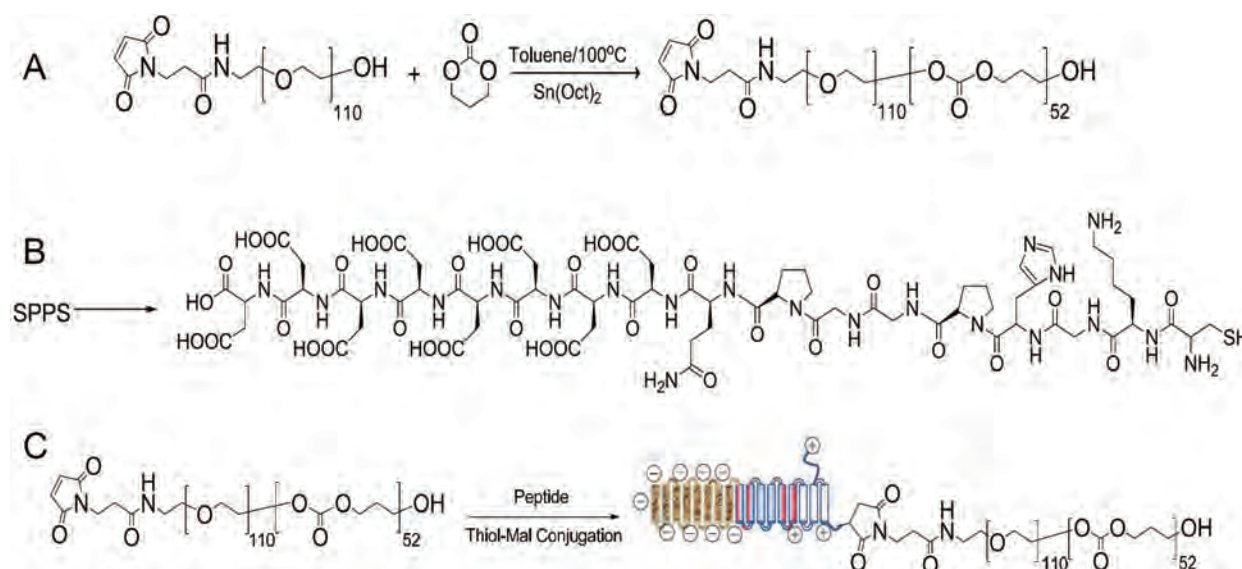


Fig. 1 Synthetic procedure and chemical structure of Mal-PEG₁₁₀-*b*-PTMC₅₂ (A), the Pep peptide (B) and Pep-*b*-PEG₁₁₀-*b*-PTMC₅₂ (C).

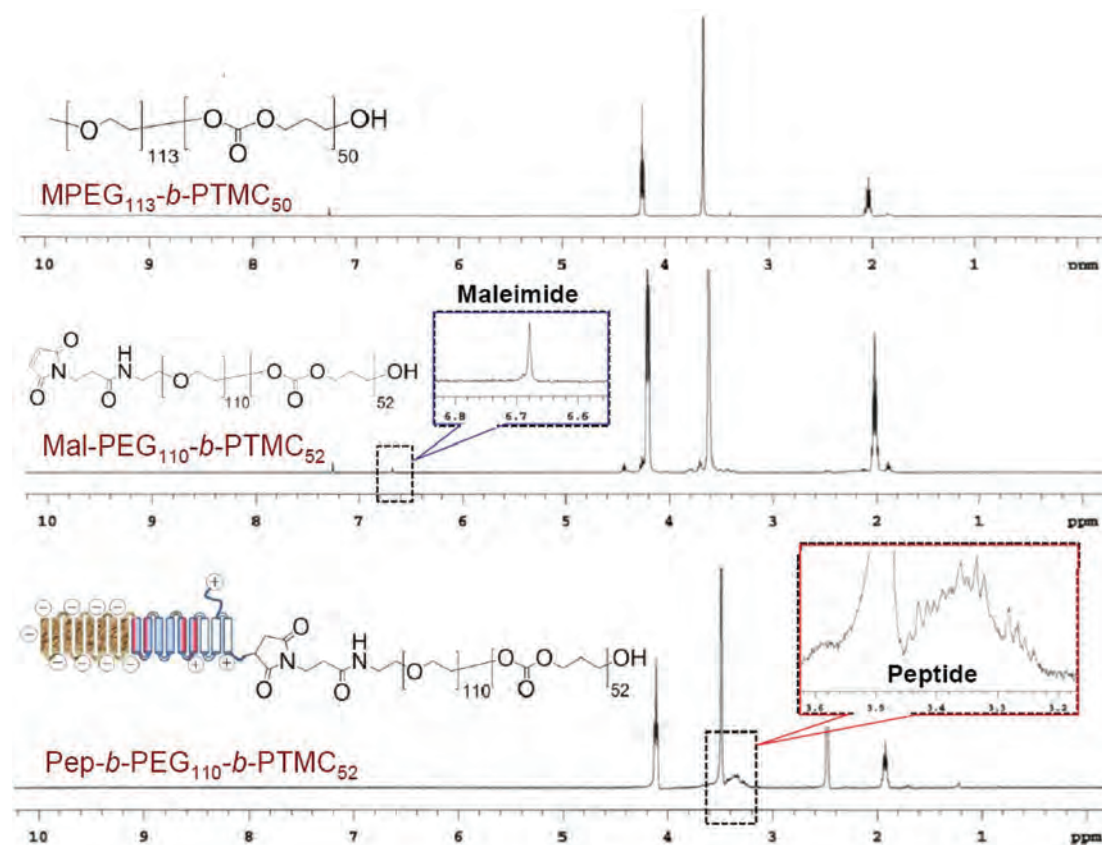


Fig. 2 ^1H NMR spectra of $\text{MPEG}_{113}\text{-}b\text{-PTMC}_{50}$ (CDCl_3), $\text{Mal-PEG}_{110}\text{-}b\text{-PTMC}_{52}$ (CDCl_3) and $\text{Pep-}b\text{-PEG}_{110}\text{-}b\text{-PTMC}_{52}$ ($\text{DMSO-}d_6$).

ance liquid chromatography (HPLC) and matrix-assisted laser desorption/ionization time-of-flight (MALDI-TOF) mass spectrometry, respectively (Fig. S1†). Via click chemistry, the chemical conjugation of CKGHPPGPGQAsp₈ to $\text{Mal-PEG}_{110}\text{-PTMC}_{52}$ afforded the target copolymer $\text{PEP-}b\text{-PEG}_{110}\text{-}b\text{-PTMC}_{52}$ (Fig. 1C), which was purified by the dialysis method (MWCO = 10 kDa) followed by ultrafiltration treatment. Successful conjugation was verified by ^1H NMR, which clearly showed the characteristic resonances of the peptide protons at $\sigma = 3.1\text{--}3.6$ ppm and complete disappearance of the maleimide-vinyl signal at $\sigma = 6.74$ ppm (Fig. 2).

As expected, $\text{Pep-}b\text{-PEG-}b\text{-PTMC}$ could readily self-assemble into the micelles in aqueous solution like many other amphiphilic copolymers,²⁴ which was confirmed by the fluorescence assay using pyrene as the probe. According to the excitation spectra of pyrene at different polymer concentrations, the critical micelle concentration (CMC) of $\text{Pep-}b\text{-PEG}_{110}\text{-}b\text{-PTMC}_{52}$ was determined to be approximately $8.02 \times 10^{-3} \text{ mg mL}^{-1}$ (Fig. 3C). The mean hydrodynamic diameter of the polymeric micelles was measured by dynamic light scattering (DLS) to be 75 ± 10 nm, showing unimodal size distribution with PDI ~ 0.1 .

In principle, the hydrophobic PTMC segments should localize in the inner core of nanomicelles while the peptide and PEG blocks form a corona-type shell due to their highly hydrophilic nature. This core-shell structure was verified by the

marked difference between its ^1H NMR spectra in DMSO (Fig. 3A) and D_2O (Fig. 3B). All the characteristic signals could be detectable in $\text{DMSO-}d_6$. Unlike this, the proton signals of the PTMC block were significantly suppressed and nearly disappeared in aqueous D_2O but those from hydrophilic blocks remained prominent. Taken together, those characterizations demonstrated that $\text{Pep-}b\text{-PEG}_{110}\text{-}b\text{-PTMC}_{52}$ was able to readily form the NVs with the core-shell architecture in the aqueous medium.

The strong binding ability of $\text{Pep-}b\text{-PEG}_{110}\text{-}b\text{-PTMC}_{52}$ micelles to hydroxyapatite (HA), commonly used as a model mineral to mimic the bone tissue mineral, was examined to preliminarily evaluate the contribution of the peptide functionality to the bone-seeking efficacy.^{5–7} A near infra-red fluorescence (NIRF) Cy5.5 probe has been one of the frequently used fluorescence indicators due to its deeper tissue penetration capacity.²⁵ Cy5.5 was encapsulated into the micellar cores by the dialysis method thus to quantitatively determine the binding affinities of the nanomicelles with and without the peptide functionality.

After incubation for 30 min, approximately 55% of the $\text{Pep-}b\text{-PEG-}b\text{-PTMC}$ micelles from the solution were rapidly bound to HA. Further incubation for 24 hours led to a moderate increase of HA-binding up to about 66% (Fig. 4). In marked contrast, less than 15% of $\text{MPEG-}b\text{-PTMC}$ micelles or free Cy5.5 were bound to HA across the entire incubation process,

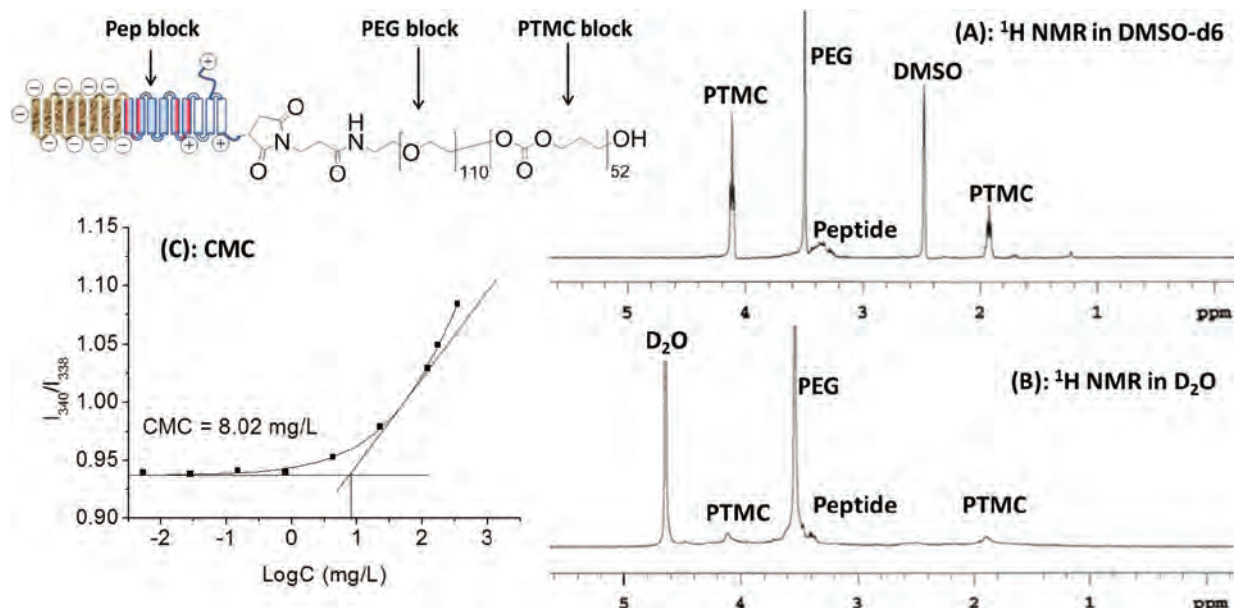


Fig. 3 ^1H NMR spectra of Pep-*b*-PEG₁₁₀-*b*-PTMC₅₂ in DMSO-d_6 (A) and D_2O (B); CMC measurement by plotting of the I_{340}/I_{338} ratio against the logarithm of the polymer concentration (C).

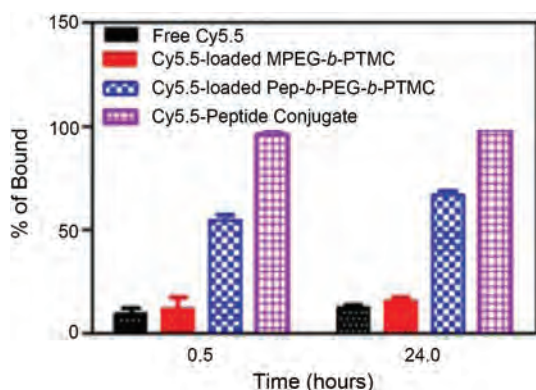


Fig. 4 Binding capacity of various Cy5.5 formulations to the bone mineral HA.

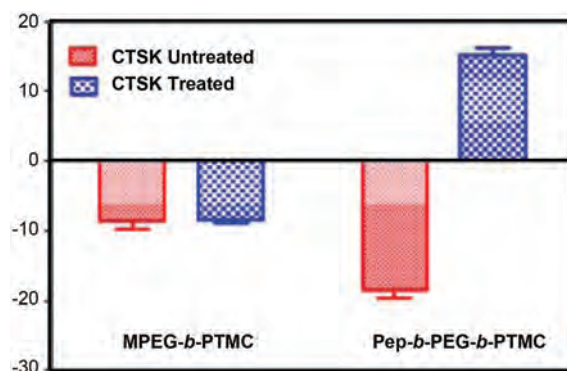


Fig. 5 Change in the zeta potential of Pep-*b*-PEG-*b*-PTMC micelles upon co-incubation with 150 nM CTSK for 30 minutes.

indicating minimal nonspecific binding to HA by the MPEG-*b*-PTMC micelles without the peptide functionality. The low-molecular-weight peptide-Cy5.5 conjugate exhibited a much stronger affinity to HA with complete binding after incubation for 30 min. Those results correlated well with the reported findings that modification with osteotropic Asp₈ would dramatically facilitate the specific binding towards HA-rich bone tissue.^{26–28} Though the outer PEG shell with steric hindrance may somewhat restrain the complete binding of Pep-*b*-PEG-*b*-PTMC micelles to HA, they still displayed dramatically enhanced HA affinities over Pep-free MPEG-*b*-PTMC micelles after all.

Typically, the decoration of bone-targeting anionic Asp₈ to NVs would disfavor the cellular uptake process due to the charge repulsion by the cell membrane, thus impairing the chemotherapy efficacy.²⁹ Within the structure of Pep-*b*-PEG-*b*-

PTMC, a CTSK cleavable substrate (HPGGPQ)^{25,30} was specially incorporated to link Asp₈ and the rest of the block copolymer. By virtue of such a CTSK-cleavable spacer, it was speculated that the bone metastatic microenvironment featured with CTSK overexpression would induce the enzymatic chain cleavage and the following removal of Asp₈ moieties from the shell periphery of the nanomicelles. Of particular interest, this CTSK-induced transition may reverse the surface charge and thus enhance the cellular uptake of the nanomicelles, which was attributed to the remaining cationic peptide residues after Asp₈ removal. To verify this speculation, the zeta potentials of polymeric micelles were measured in the presence and absence of CTSK, respectively. Following 30 min treatment with CTSK, the zeta potential of Pep-*b*-PEG-*b*-PTMC micelles had an instantly marked promotion from -18.5 ± 1.9 mV to 15.2 ± 1.8 mV (Fig. 5). Nevertheless, the control experiment without CTSK treatment afforded nearly no variation of the

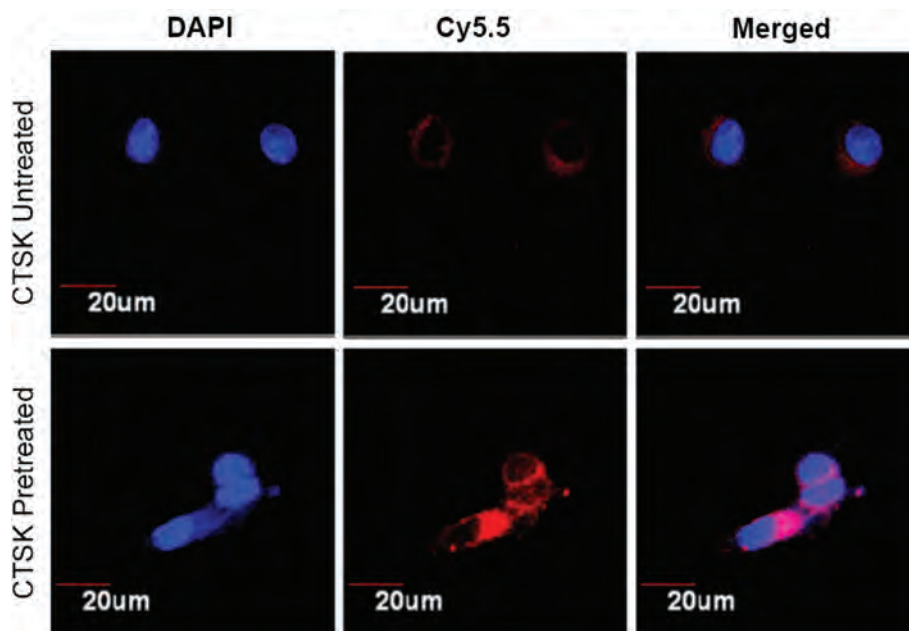


Fig. 6 CLSM images of MCF-7 cells incubated with Pep-*b*-PEG-*b*-PTMC micelles with or without CTSK treatment.

zeta potential. Apparently, it is just CTSK exposure that allowed the charge reversal of the Pep-*b*-PEG-*b*-PTMC micelles.

For comparison, the CTSK-responsiveness of the zeta potential was also tested for MPEG-*b*-PTMC micelles with the identical CTSK treatment. No apparent variation was found upon CTSK exposure and the micellar zeta potential remained almost constant within a narrow range from -8.6 ± 2.1 mV to -8.4 ± 0.7 mV. Those results pointed out that the introduction of the CKGHPPGPPQAsp₈ functionality indeed played a dominant role in the CTSK-induced negative-to-positive charge conversion of Pep-*b*-PEG-*b*-PTMC micelles.

To evidence the contribution of CTSK-responsive charge reversal to the intracellular internalization, confocal laser scanning microscopy (CLSM) was used to investigate the cellular uptake of polymeric micelles under the conditions with or without CTSK treatment. The nanomicelles assembled from Pep-*b*-PEG-*b*-PTMC were loaded with the Cy5.5 fluorescence indicator, followed by incubation with MCF-7 cells in the presence or absence of CTSK. Following 30 min incubation, the MCF-7 cells were subjected to CLSM observation. As shown in Fig. 6, very weak red fluorescence can be detected in the cells co-incubated with Pep-*b*-PEG-*b*-PTMC micelles in the medium free of CTSK, indicating that few fluorescence-labeled micelles were taken up by MCF-7 cells under this condition. The poor cellular uptake of untreated micelles was reasonably expected, because it was difficult for the negatively charged NVs to be intracellularly internalized owing to the charge repulsion effect. However, upon CTSK exposure, significant fluorescence enhancement was observed from the CLSM images. This was ascribed to the cationic nature of the micelles resulting from CTSK-induced charge-reversal, which was known to favor the approach of NVs to the negatively charged cell membranes and thus facilitate their cellular uptake. For the control of MPEG-*b*-

PTMC micelles, it is not strange that a minimal difference was observed between the CLSM images obtained before and after CTSK treatment (data not shown).

The CTSK-dependent cellular uptake of Pep-*b*-PEG-*b*-PTMC nanomicelles seemed very attractive in terms of the chemotherapy potential for bone metastases. It can be noted that those nanomicelles would be hardly taken up by the cells in the normal tissues due to the lack of CTSK expression; once the nanoparticles were guided and accumulated in CTSK-rich environments (*i.e.*, CTSK over-expressed bone metastases lesions), however, the transition to cationic NVs would considerably facilitate the entry into the neighboring tumor cell and thus allow the effective treatment with lower systematical biotoxicity.

To further explore the potential of Pep-*b*-PEG-*b*-PTMC as a drug carrier, an anticancer drug DOX was used as a model drug to investigate the drug loading and release properties. Poorly water-soluble DOX was encapsulated into the micelles of Pep-*b*-PEG-*b*-PTMC or MPEG-*b*-PTMC by the dialysis method. Typical DOX-loading capacity for mPEG-*b*-PTMC micelles was determined as $7.5 \pm 0.5\%$ and $22.7 \pm 1.5\%$ for DLC (drug loading content) and DLE (drug loading efficiency), respectively. Dramatic increases of DLC ($30.0 \pm 1\%$) and DLE ($90.1 \pm 2\%$) were observed when Pep-*b*-PEG-*b*-PTMC was used as the drug carrier. Such a high loading efficiency may be the result of the charged nature of Pep-*b*-PEG-*b*-PTMC, for which the outer PEG chains extend more freely and more aggregation numbers per micelle are required to ensure the hydrophilic-hydrophobic balance in the aqueous medium. Thus the DOX drug molecules enter the micelle interior more readily and the larger core is more capable of containing more drug cargos. This is consistent with the finding reported in the literature that charged NVs generally possess high DOX-loading

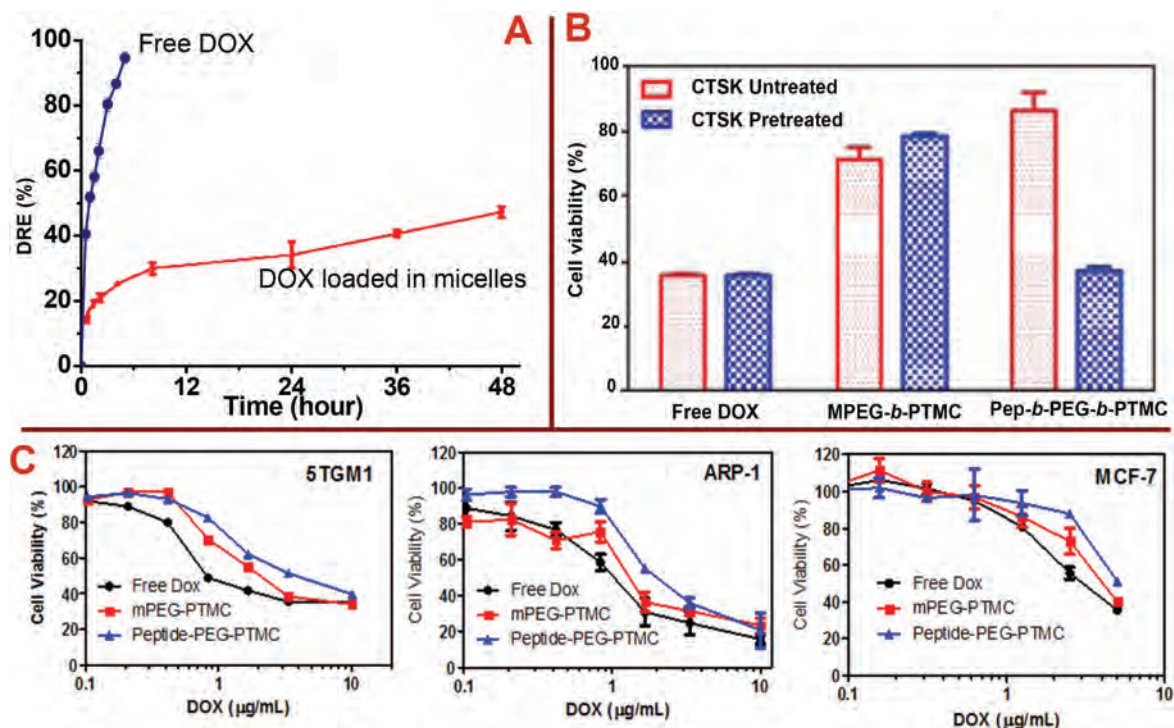


Fig. 7 (A) Cumulative DOX release from the polymeric micelles at pH = 7.4. (B) Cell viability of 5TGM1 cells after incubation with free DOX, DOX-loaded MPEG-b-PTMC nanomicelles, and DOX-loaded Pep-b-PEG-b-PTMC nanomicelles at the same DOX concentration of 1 µg mL⁻¹. Formulations were pre-treated with (blue) or without (red) 150 nM CTSK for 30 minutes. (C) *In vitro* inhibition of 5TGM1, ARP-1 and MCF-7 cells after 48 h incubation with free DOX or DOX-loaded NPs at various doses; data are presented as the average ± standard deviation (*n* = 3).

capacity.^{13,31–33} The representative example is that the highest drug loading (47% w/w) of DOX-loaded micelles reported to date was achieved when anionic polymeric glutamic acid (PGA) was used as a building block within PTMC-*b*-PGA.³¹ The *in vitro* drug release study was performed under a simulated physiological condition (pH 7.4). Fig. 7A compares the drug release profiles between the free DOX and the DOX loaded in Pep-*b*-PEG-*b*-PTMC micelles. The results suggested that DOX-loaded micelles exhibited a moderately rapid release in the first stage (around 10%) followed by a sustained release period. The sustained DOX release could be attributed to the hydrophobic interaction of drug molecules with the hydrophobic core of the polymeric micelles.

The *in vitro* cytotoxicity profiles of free DOX or DOX-loaded polymeric micelles were evaluated in the cultured cells including myeloma (the most frequent cancer type for bone metastases) suspension cell lines (5TGM1 and ARP-1) and a breast cancer (the second most frequent cancer type for bone metastases) adherent cell line (MCF-7) by the PrestoBlue™ (Invitrogen) assay. The PrestoBlue assay performed very well to quantitatively measure cell proliferation and to establish the relative viability of both suspension and adherent cells. As shown in Fig. 7C, free DOX exhibited a relatively higher toxic effect than that of both DOX-loaded Pep-free and Pep-functionalized polymeric micelles after 4 h culture. The lowered potency of DOX after encapsulation into the micelles was probably due to the sustained release pattern of DOX from the

micelles and delayed drug efficacy in the cultured cells. Overall, DOX-loaded Pep-PEG-*b*-PTMC nanomicelles showed lower cytotoxicity than the Pep-free MPEG-*b*-PTMC micelles. Since the CTSK activity has strong association with the interactions between tumor cells and the bone microenvironment, to give more exact information about the influence of CTSK-responsive charge-reversal on the biological properties of Pep-*b*-PEG-*b*-PTMC micelles, the 5TGM1 cytotoxicity of the DOX-loaded micelles was comparatively explored after a short co-incubation period of 30 min under the conditions with or without CTSK treatment. At an equivalent DOX dose (1 µg mL⁻¹), drug-loaded Pep-*b*-PEG-*b*-PTMC micelles showed lower capability to induce the cell death than the Pep-free MPEG-*b*-PTMC control. CTSK treatment resulted in significant improvement of the drug efficacy in the case of Pep-*b*-PEG-*b*-PTMC micelles (Fig. 7B), which was even comparable to the acute toxicity of free DOX. Noticeably, the CTSK-responsive improvement of toxic effect was not observed for free DOX or DOX-loaded mPEG-*b*-PTMC micelles. This marked contrast manifested a close tie between the CTSK responsiveness and the Pep functionality in the micelles, which contributed much to the enhanced drug efficacy. In combination with the result of intracellular internalization obtained from confocal images, it is naturally inferred that the anionic nature associated with the targeting Asp₈ moieties would disfavor the intracellular internalization of the Pep-*b*-PEG-*b*-PTMC micelles and therefore impair the drug efficacy, whereas CTSK-responsive

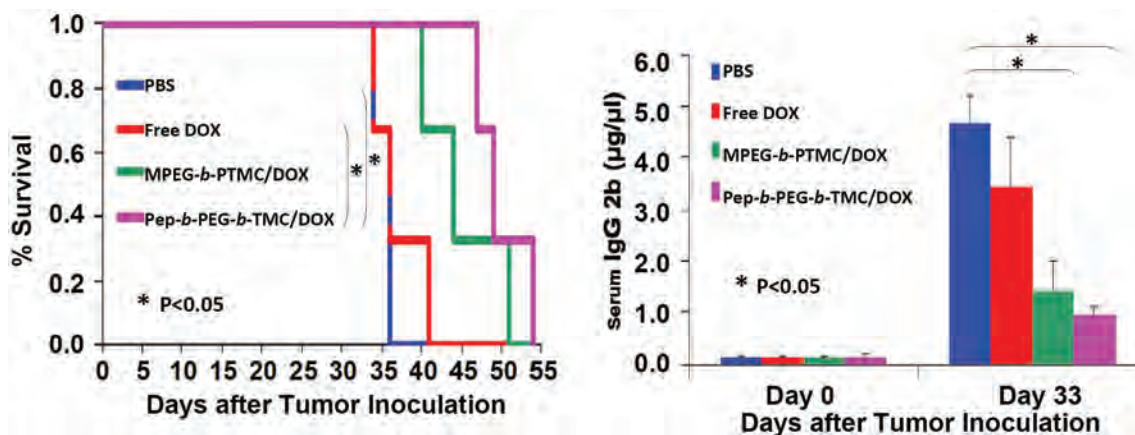


Fig. 8 (A) Efficacy of free DOX or DOX-loaded nanomicelles in bone metastatic 5TGM1 mice bearing myeloma; (B) Kaplan–Meier survival curves of mice following tumor injection and treatments. Relative tumour burden in mice was determined by the IgG 2b level in sera. * $P < 0.05$ ($n = 3$).

charge reversal may more or less overcome this biological barrier.

Despite the advance of drug delivery nanosystems for bone metastases, to the best of our knowledge, nearly no *in vivo* efficacy evaluation in animal studies have yet been reported. This could be in part ascribed to the limited availability of suitable detection means for the disease progression of bone metastases. Herein, a preliminary *in vivo* study was conducted to test the efficacy of DOX-loaded Pep-b-PEG-b-PTMC nanomicelles in a 5TGM1-induced myeloma-bearing mice model. Multiple myeloma is the most frequent cancer-induced osteolytic disease,^{1,2} which intends to invade skeletal tissues in a similar mechanism to cancer cells that interact with the bone marrow microenvironment.³⁴ Likewise, the interactions between myeloma cells and osteoclasts yield substantial cathepsin K up-regulation, resulting in osteolytic lesions.³⁵ Noticeably, the real-time tumor burden in 5TGM1 mice can be easily monitored by measuring the 5TGM1 idiotype (IgG2b) in mouse sera.³⁶ The higher IgG2b level in sera, the bigger tumor in the body. This is a distinct advantage since the progression of other types of cancers can only be identified with advanced imaging modalities (μ CT, X-ray, etc.).³⁷ Myeloma-bearing 5TGM1 mice were established through inoculation of 5TGM1 cells (1×10^6 cells in 100 μ L PBS) *via* tail vein injection, and the tumors were allowed to develop and grow for one week before initiating study treatments. The mice were injected twice weekly with different therapeutic formulations at an equivalent DOX dose (0.75 mg kg^{-1}) or blank PBS, and the IgG2b level in sera was monitored by ELISA measurements.

As shown in Fig. 8A, the myeloma-bearing 5TGM1 mice group treated with DOX-loaded Pep-b-PEG-b-PTMC micelles showed prolonged survival rate in comparison with the control groups with the administration of DOX-loaded MPEG-b-PTMC micelles, free DOX or blank PBS. Since the tumor burden was positively correlated with the IgG2b level, the data in Fig. 8B distinctly indicated that Pep-b-PEG-b-PTMC/DOX nanotherapeutic was meanwhile more effective to slow down tumor growth than the other formulations with the equivalent DOX

dose. Together with the *in vitro* results, the observed improvement of both *in vivo* systematic biosafety and drug efficacy manifested the superiority of our pathology-specific design by combining both the advantages of efficient DOX delivery to bone metastatic tissues and CTSK-responsive cellular uptake of DOX within lesion sites.

4. Conclusions

Cancer induced bone metastases often lead to substantial morbidity and mortality, which remain a significant therapeutic challenge for cancer treatment. In attempts to address this challenge, a peptide decoration strategy was proposed to render the NVs both the bone-seeking function and the charge-reversal capability in response to the pathological microenvironment. The nanomicelles self-assembled from the Pep-b-PEG-b-PTMC polymer showed strong apatite binding affinity and readily underwent the negative-to-positive charge reversal upon exposure to CTSK, an overexpressed enzyme in bone metastatic microenvironments. This unique characteristic led to dramatically enhanced cellular uptake within bone metastatic sites in a pathology-responsive manner, thus improving the drug efficacy of the loaded DOX *in vitro* and *in vivo*. Although our attempt presented herein for the enhanced bone metastasis chemotherapy is still in an initial stage, the obtained *in vivo* and *in vitro* results are fairly encouraging. More attractively, the success of this strategy may open a new avenue to chemotherapy for the malignant diseases in bone tissue, including but not limited to bone metastases, provided that the development of therapy for those diseases involves overexpression of certain enzymes.

Acknowledgements

This research was supported by NIH (R01CA166941, X. Wang), the Department of Defense (W81XWH1110307 and

W81XWH1310240, X. Wang), the University of Utah CCTS Pilot Award (U59004183, X. Wang) from the NIH National Center for Research Resources (UL1RR025746), the TRP Award (6246-11, F. Zhan) from the Leukemia & Lymphoma Society, and the National Natural Science Foundation of China (grant no. 21374085, J. Feng).

Notes and references

- 1 G. D. Roodman, *N Engl. J. Med.*, 2004, **350**(16), 1655–1664.
- 2 L. S. Loftus, S. Edwards-Bennett and G. H. Sokol, *Cancer Control*, 2012, **19**(2), 145–153.
- 3 C. M. Bagi, *Adv. Drug Delivery Rev.*, 2005, **57**(7), 995–1010.
- 4 R. E. Coleman, *Nat. Rev. Clin. Oncol.*, 2012, **9**(2), 76–78.
- 5 D. Wang, S. C. Miller, P. Kopeckova and J. Kopecek, *Adv. Drug Delivery Rev.*, 2005, **57**(7), 1049–1076.
- 6 K. Miller, R. Erez, E. Segal, D. Shabat and R. Satchi-Fainaro, *Angew. Chem., Int. Ed.*, 2009, **48**(16), 2949–2954.
- 7 D. Wang, S. C. Miller, L. S. Shlyakhtenko, A. M. Portillo, X. M. Liu, K. Papangkorn, P. Kopeckova, Y. Lyubchenko, W. I. Higuchi and J. Kopecek, *Bioconjugate Chem.*, 2007, **18**(5), 1375–1378.
- 8 Q. Zhao, Y. Jia and Y. Xiao, *Biochem. Biophys. Res. Commun.*, 2009, **380**(4), 721–723.
- 9 C. Le Gall, A. Bellahcene, E. Bonnelye, J. A. Gasser, V. Castronovo, J. Green, J. Zimmermann and P. Clezardin, *Cancer Res.*, 2007, **67**(20), 9894–9902.
- 10 R. N. Pearce, *Clin. Breast Cancer*, 2007, **8**, S35–S45.
- 11 C. Le Gall, E. Bonnelye and P. Clezardin, *Curr. Opin. Support. Palliat. Care*, 2008, **2**(3), 218–222.
- 12 J. Sturge, M. P. Caley and J. Waxman, *Nat. Rev. Clin. Oncol.*, 2011, **8**(6), 357–368.
- 13 J. Z. Du, T. M. Sun, W. J. Song, J. Wu and J. Wang, *Angew. Chem., Int. Ed.*, 2010, **49**(21), 3621–3626.
- 14 Y. Lee, T. Ishii, H. Cabral, H. J. Kim, J. H. Seo, N. Nishiyama, H. Oshima, K. Osada and K. Kataoka, *Angew. Chem., Int. Ed.*, 2009, **48**(29), 5309–5312.
- 15 Y. Lee, K. Miyata, M. Oba, T. Ishii, S. Fukushima, M. Han, H. Koyama, N. Nishiyama and K. Kataoka, *Angew. Chem., Int. Ed.*, 2008, **47**(28), 5163–5166.
- 16 P. S. Xu, E. A. Van Kirk, Y. H. Zhan, W. J. Murdoch, M. Radosz and Y. Q. Shen, *Angew. Chem., Int. Ed.*, 2007, **46**(26), 4999–5002.
- 17 T. Ariga, T. Takata and T. Endo, *Macromolecules*, 1997, **30**(4), 737–744.
- 18 A. P. Dove, R. C. Pratt, B. G. Lohmeijer, R. M. Waymouth and J. L. Hedrick, *J. Am. Chem. Soc.*, 2005, **127**(40), 13798–13799.
- 19 H. R. Kricheldorf, I. Kreiser-Saunders and A. Stricker, *Macromolecules*, 2000, **33**(3), 702–709.
- 20 J. Z. Du, D. P. Chen, Y. C. Wang, C. S. Xiao, Y. J. Lu, J. Wang and G. Z. Zhang, *Biomacromolecules*, 2006, **7**(6), 1898–1903.
- 21 H. Z. Pan, P. Kopeckova, D. Wang, J. Y. Yang, S. Miller and J. Kopecek, *J. Drug Target*, 2006, **14**(6), 425–435.
- 22 J. Feng, X. Z. Zhang and R. X. Zhuo, *Prog. Polym. Sci.*, 2012, **37**(2), 211–236.
- 23 F. Nederberg, B. G. G. Lohmeijer, F. Leibfarth, R. C. Pratt, J. Choi, A. P. Dove, R. M. Waymouth and J. L. Hedrick, *Biomacromolecules*, 2007, **8**(1), 153–160.
- 24 L. Liu, K. Xu, H. Wang, P. K. Tan, W. Fan, S. S. Venkatraman, L. Li and Y. Y. Yang, *Nat. Nanotechnol.*, 2009, **4**(7), 457–463.
- 25 K. M. Kozloff, L. Quinti, S. Patntirapong, P. V. Hauschka, C. H. Tung, R. Weissleder and U. Mahmood, *Bone*, 2009, **44**(2), 190–198.
- 26 M. B. Murphy, J. D. Hartgerink, A. Goepferich and A. G. Mikos, *Biomacromolecules*, 2007, **8**(7), 2237–2243.
- 27 S. Kasugai, R. Fujisawa, Y. Waki, K. Miyamoto and K. Ohya, *J. Bone Miner. Res.*, 2000, **15**(5), 936–943.
- 28 D. Wang, S. Miller, M. Sima, P. Kopeckova and J. Kopecek, *Bioconjugate Chem.*, 2003, **14**(5), 853–859.
- 29 K. Xiao, Y. Li, J. Luo, J. S. Lee, W. Xiao, A. M. Gonik, R. G. Agarwal and K. S. Lam, *Biomaterials*, 2011, **32**(13), 3435–3446.
- 30 F. A. Jaffer, D. E. Kim, L. Quinti, C. H. Tung, E. Aikawa, A. N. Pande, R. H. Kohler, G. P. Shi, P. Libby and R. Weissleder, *Circulation*, 2007, **115**(17), 2292–2298.
- 31 C. Sanson, C. Schatz, J. F. Le Meins, A. Soum, J. Thevenot, E. Garanger and S. Lecommandoux, *J. Controlled Release*, 2010, **147**(3), 428–435.
- 32 C. Yang, J. Tan, W. Cheng, A. Attia, C. Tan, Y. Ting, A. Nelson, J. L. Hedrick and Y. Y. Yang, *Nano Today*, 2009, **5**, 515–523.
- 33 N. Wiradharma, Y. Zhang, S. Venkataraman, J. L. Hedrick and Y. Y. Yang, *Nano Today*, 2009, **4**(4), 302–317.
- 34 J. A. Fowler, C. M. Edwards and P. I. Croucher, *Bone*, 2011, **48**(1), 121–128.
- 35 M. Hecht, I. von Metzler, K. Sack, M. Kaiser and O. Sezer, *Exp. Cell Res.*, 2008, **314**(5), 1082–1093.
- 36 B. O. Oyajobi, G. Franchin, P. J. Williams, D. Pulkrabek, A. Gupta, S. Munoz, B. Grubbs, M. Zhao, D. Chen, B. Sherry and G. R. Mundy, *Blood*, 2003, **102**(1), 311–319.
- 37 T. J. Rosol, S. H. Tannehill-Gregg, B. E. LeRoy, S. Mandl and C. H. Contag, *Cancer*, 2003, **97**(3), 748–757.